

Development of Functional and Scratch Resistant UV Curable Wood Coatings

Alin Guctas², Duygu Sevinc Esen¹, Ebru Yildirim², Ebru Erguven¹, Deniz Er¹, Nergis Arsu²

¹Kayalar Kimya San. ve Tic. A.S. Tuzla, Istanbul, 34956, Turkey


²Department of Chemistry, Yildiz Technical University, Davutpasa Campus Istanbul, 34220, Turkey

Dr. Duygu SEVİNÇ ESEN

Innovation Projects R&D Senior Specialist

GENÇ Wood Coating Systems

Table of Contents

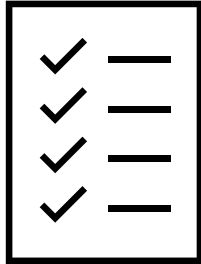

General Information About Coatings

UV Curing Technology

Functional Coatings and Nanoparticles


Experimental Part

Results and Discussion


Conclusion

Acknowledgement

1

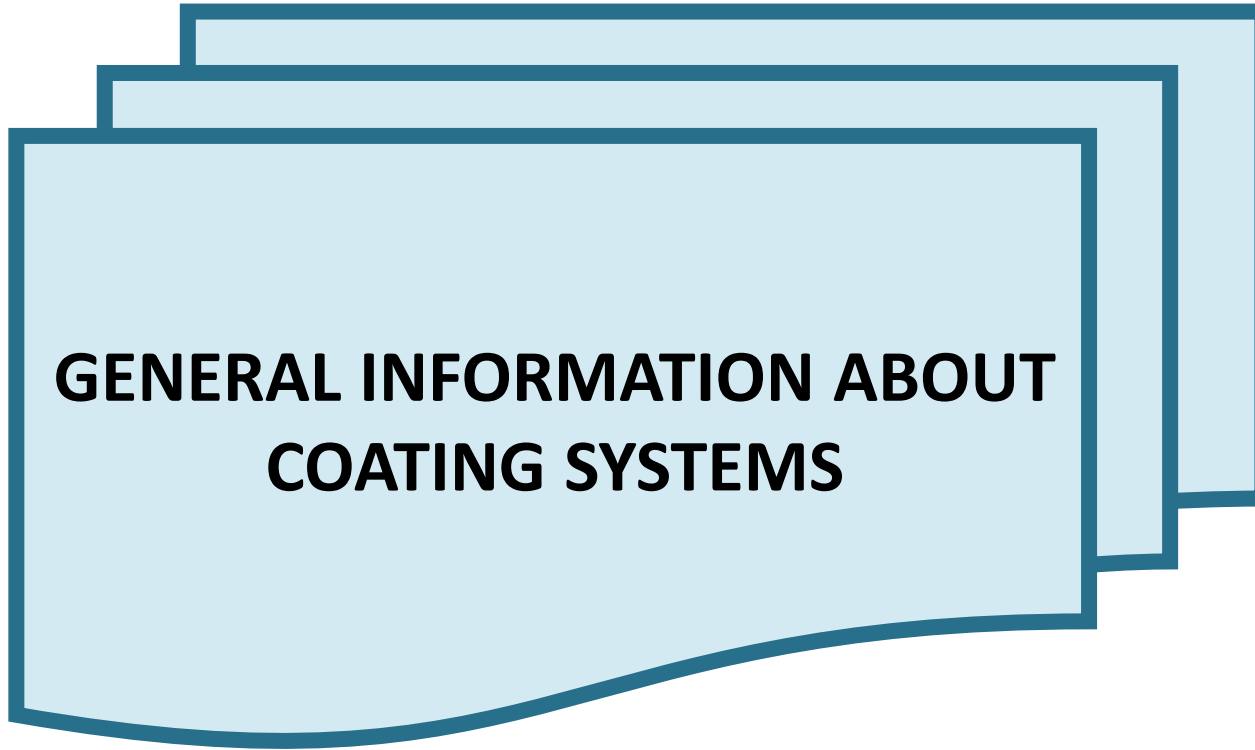

Main Components and Purposes of Coatings

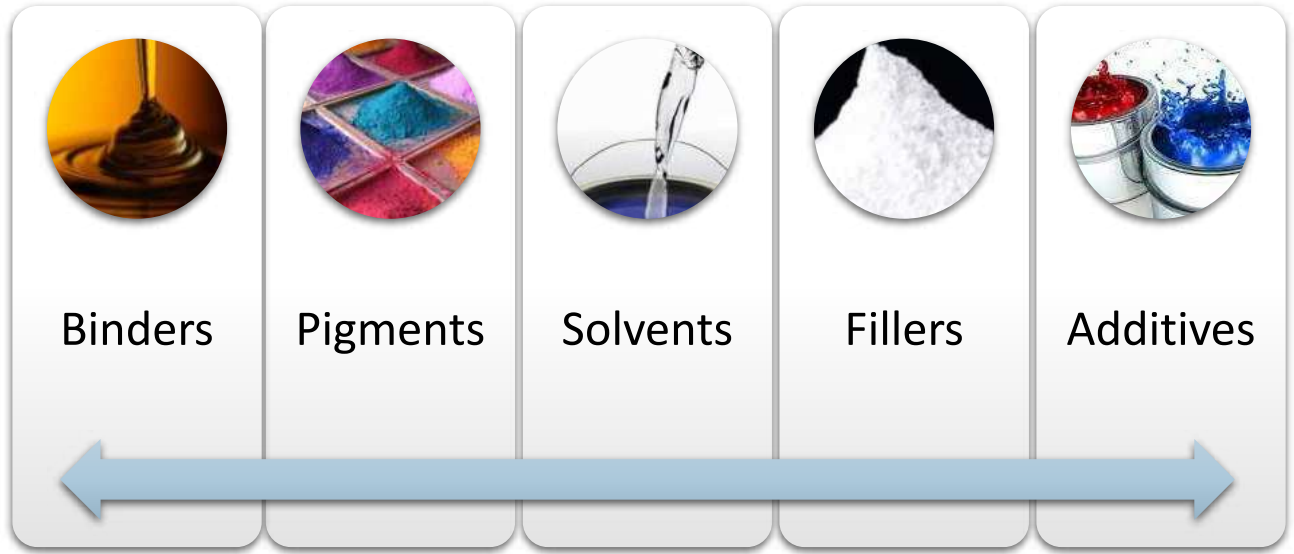

Automotive coatings



Aircraft coatings



Textile coatings



Architectural coatings



Metal coatings



Wood coatings

Wood Coatings Depending on the Binder Type

Cellulosic coatings

Acrylic coatings (1K ve 2K)

Synthetic coatings

Epoxy coatings

Polyurethane coatings (1K ve 2K)

Waterbased coatings (PUD and acrylic 1K, 2K)

UV curable coatings


Powder coatings

Acid curable coatings



Disadvantages of Solventbased Systems and Alternatives

VOC Sources

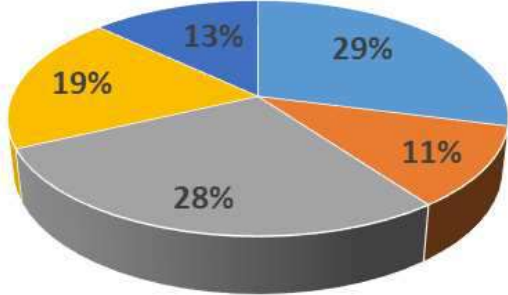


- Use of solvent
- Vehicles
- Other
- Industrial Processes
- Home / Office Equipments

<https://epa.gov>





- UV curable systems
- Waterbased systems
- % 100 solid systems (Powder coatings)
- High solid systems
- Biobased systems

2

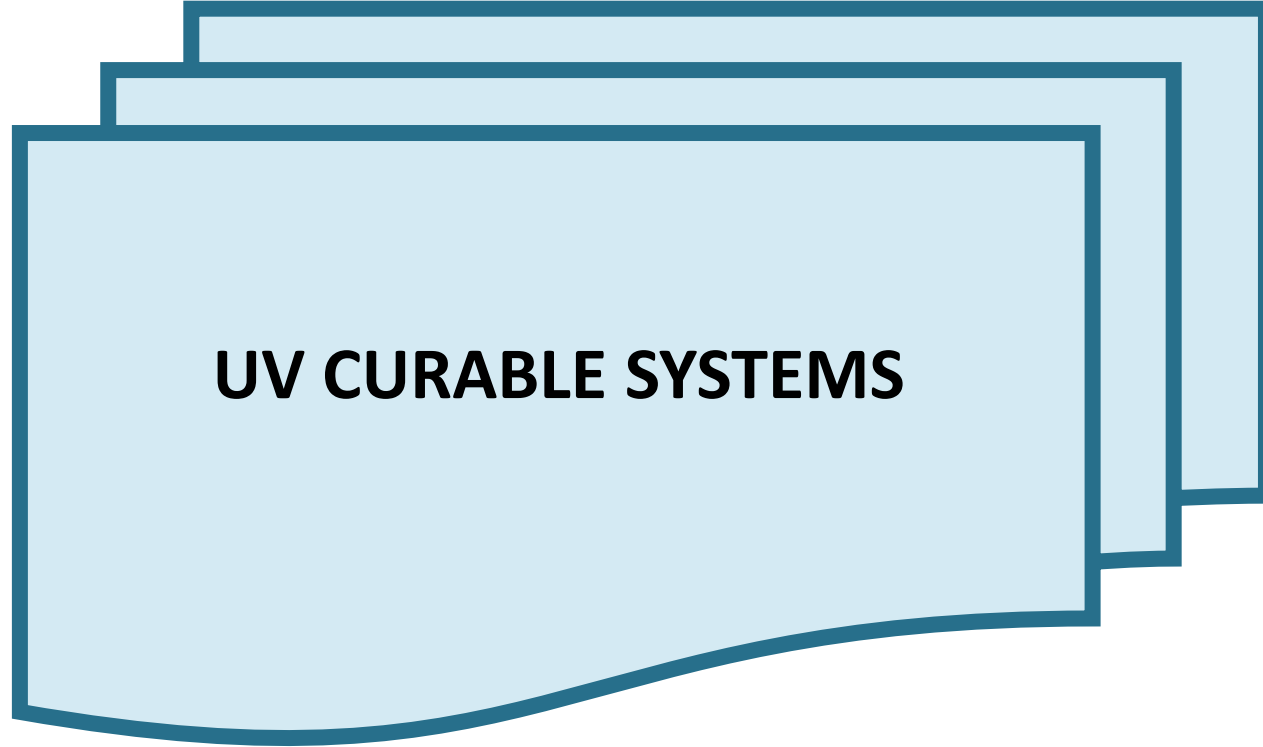

Electromagnetic Spectrum & UV Region

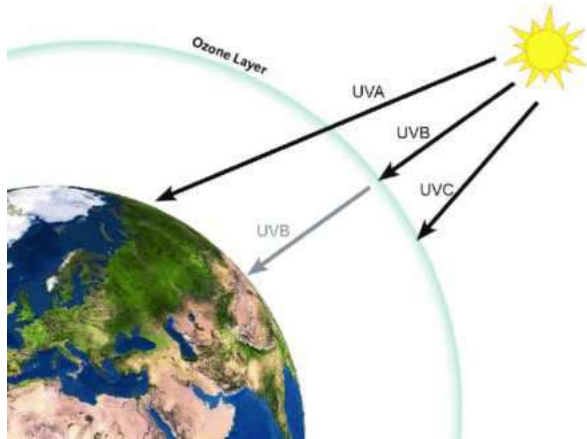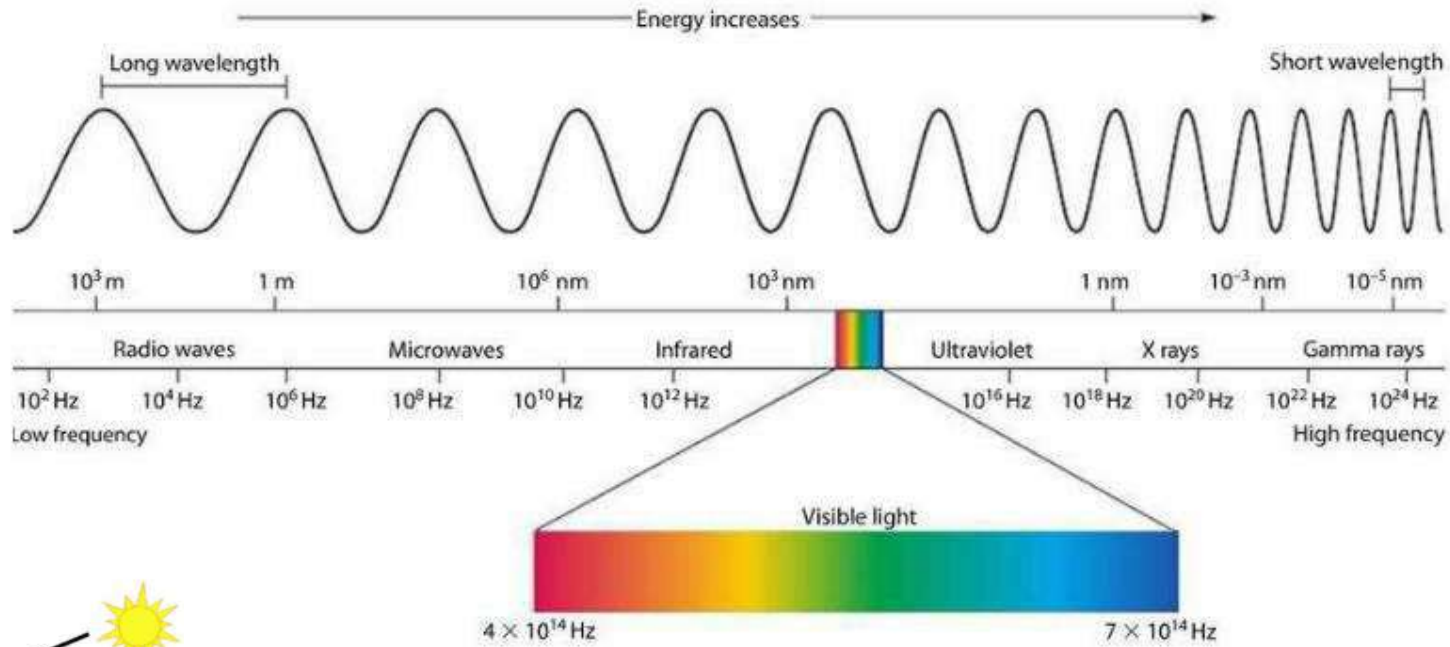


UV Region	Wavelength (nm)	Characteristic Properties	Application Area
Visible Region	780-380		Adhesives
UV-A	380-315	Deep Curing	Inks and Coatings
UV-B	315-280		Varnishes
UV-C	280-200	Surface Curing	Sterilization
UV-V	200-100	Absorption by Oxygen	Excimer Lamps



Components of UV Curable Systems

Oligomers	Monomers (Reactive diluents)	Photoinitiators	Additives
<ul style="list-style-type: none"> <input type="checkbox"/> High molecular weight compounds <input type="checkbox"/> Reducing viscosity <input type="checkbox"/> Participate in crosslinking reactions 	<ul style="list-style-type: none"> <input type="checkbox"/> Low molecular weight compounds <input type="checkbox"/> Reducing viscosity <input type="checkbox"/> Participate in crosslinking reactions 	<ul style="list-style-type: none"> <input type="checkbox"/> Initiation of the polymerization <input type="checkbox"/> Can be different chemical structure 	<ul style="list-style-type: none"> <input type="checkbox"/> Improving the performance of the coating <input type="checkbox"/> Can be different type
<ul style="list-style-type: none"> ✓ Epoxy acrylates ✓ Polyester acrylates ✓ Urethane acrylates ✓ Polyether acrylates 	<ul style="list-style-type: none"> ✓ TPGDA (Tripropylene glycol diacrylate) ✓ DPGDA Dipropylene glycol diacrylate ✓ HDDA (Hexandiol diacrylate) ✓ LA (Lauryl acrylate) ✓ IBOA (Isobornyl acrylate) 	<ul style="list-style-type: none"> ✓ Type- 1 PI ✓ Type-2 PI ✓ One Component Type-2 PI ✓ Polymeric PI 	<ul style="list-style-type: none"> ✓ Dispersing agents ✓ Defoamers ✓ Rheology modifiers ✓ Matting agents ✓ Fillers ✓ Anti-sagging agents ✓ Matlaştırıcılar ✓ UV Stabilizers ✓ Adhesion promoters




Principles of UV Curable Systems

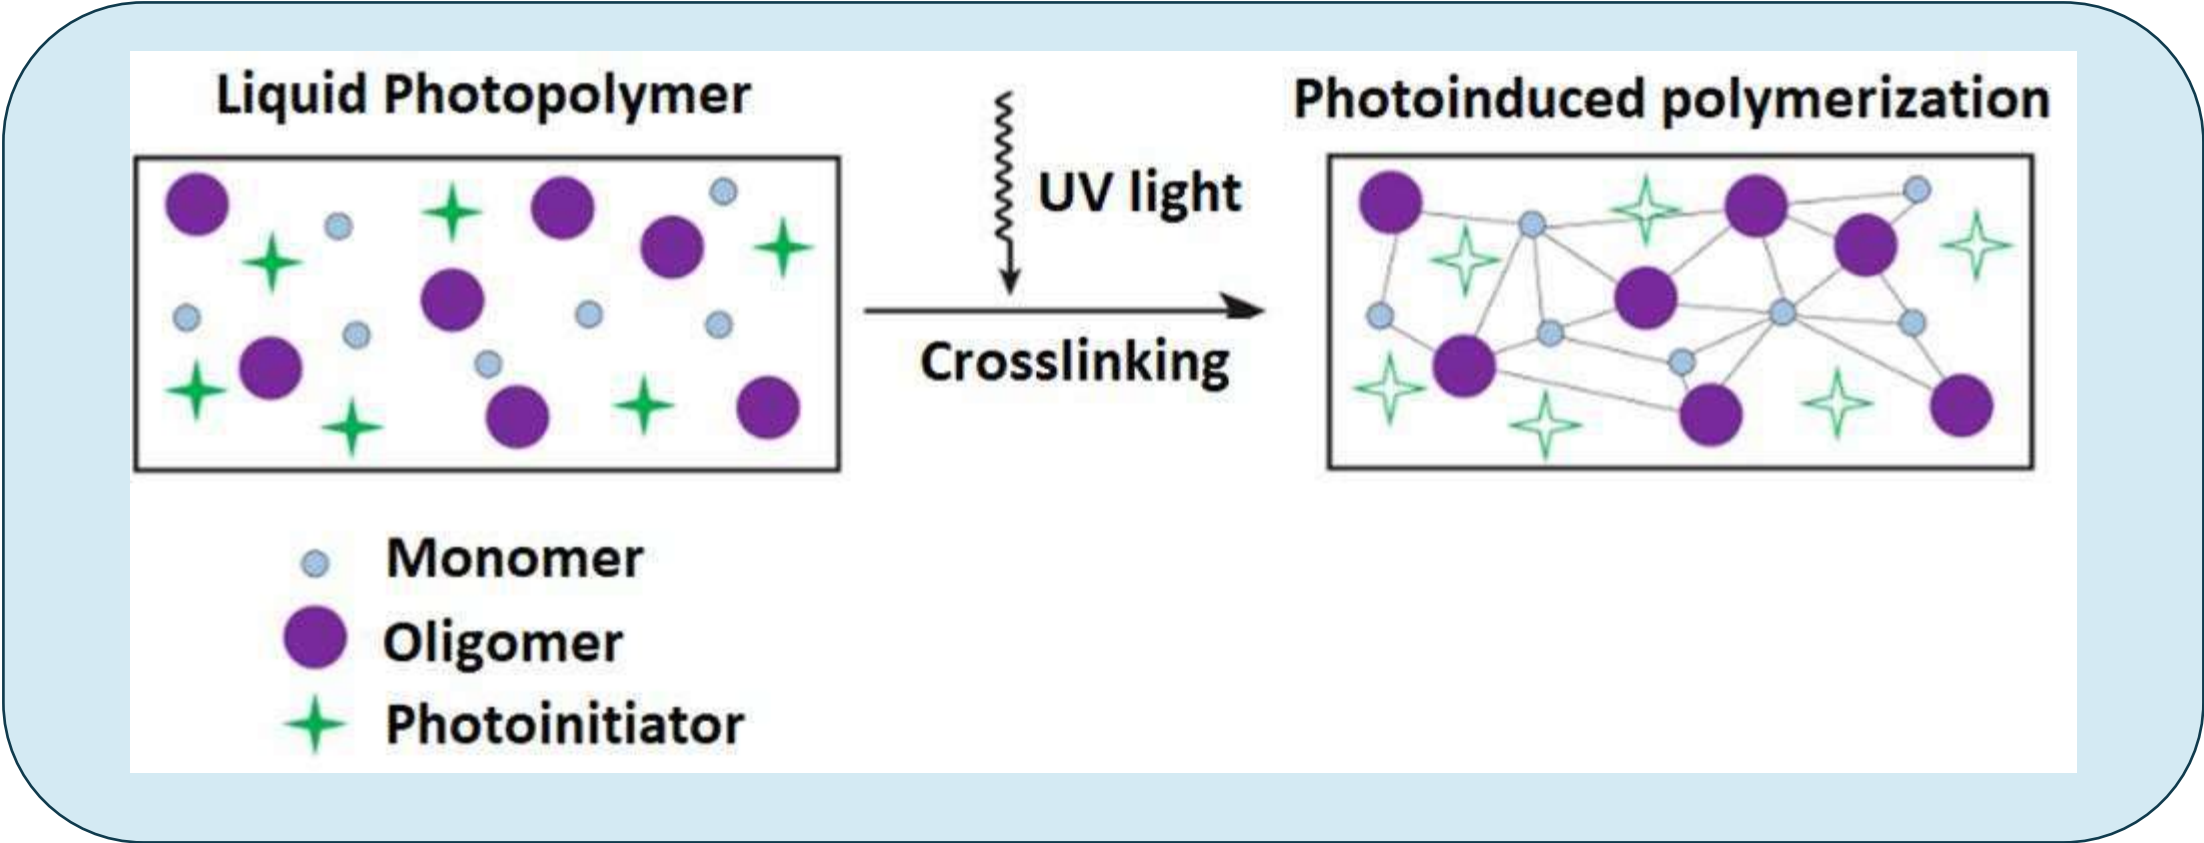




Free Radical Polymerization Mechanism




$\xrightarrow{\text{by disproportionation}}$

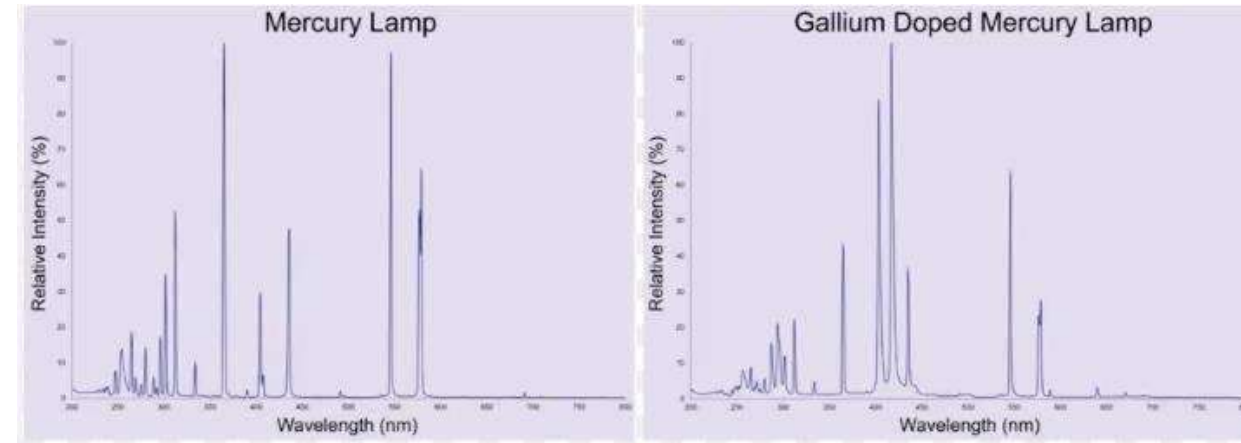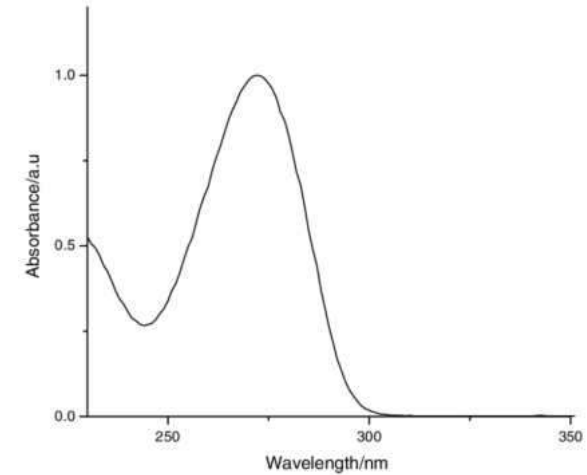


Advantages of UV Curable Systems

Environmental	<ul style="list-style-type: none"> ✓ Very low VOC emissions ✓ Minimum waste ✓ More sustainable 	
Production & Application	<ul style="list-style-type: none"> ✓ Very fast curing at room temperature ✓ Need little space for applications ✓ High production capacity with automation 	
Product Performance	<ul style="list-style-type: none"> ✓ Ease of stacking of products ✓ Excellent strength, chemical resistance ✓ High scratch resistance 	

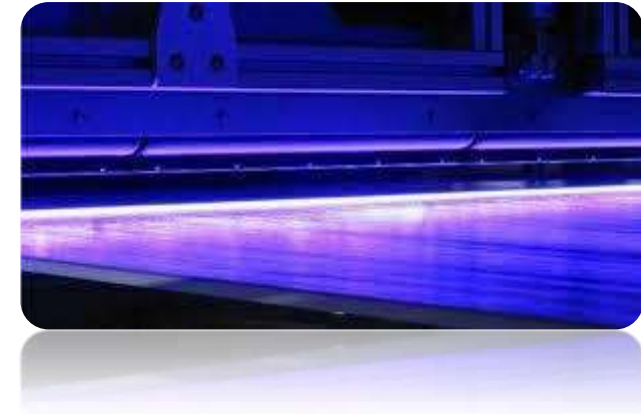



Usage Areas of UV Curable Systems

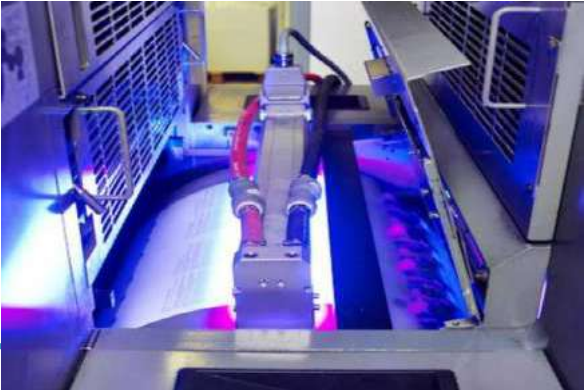

3




**FUNCTIONAL COATINGS &
NANOPARTICLES**

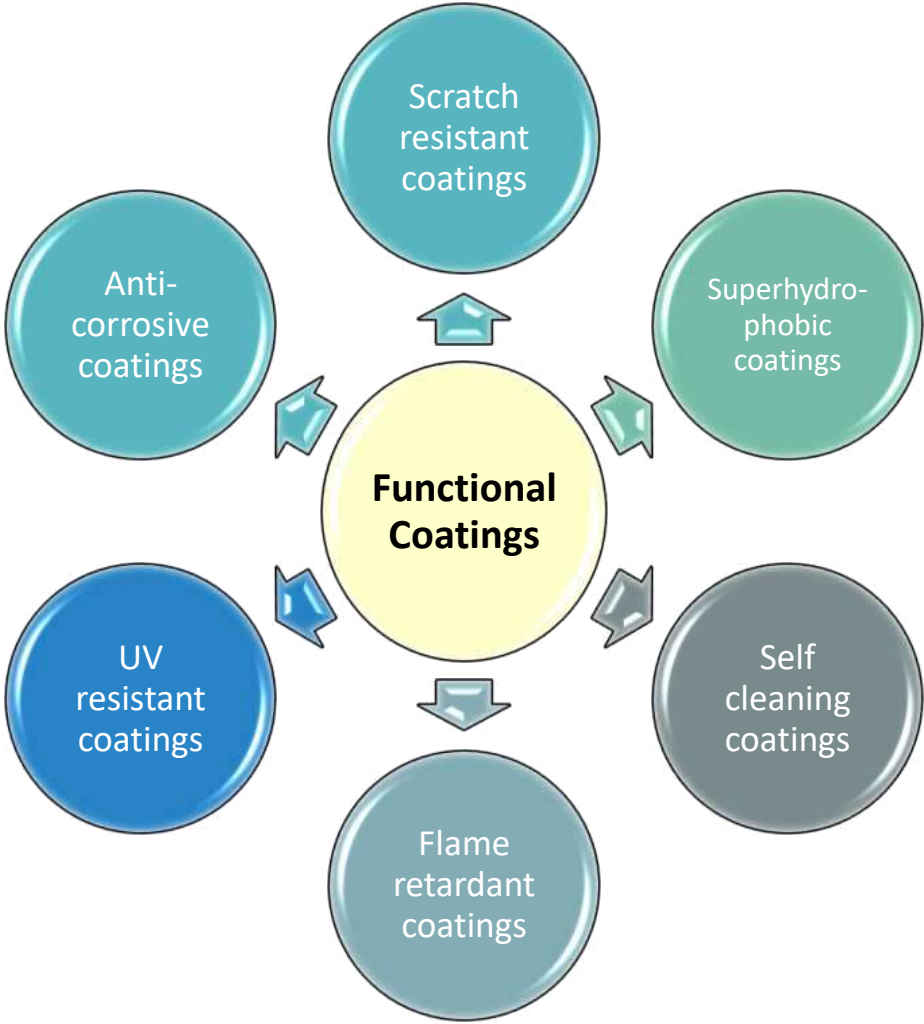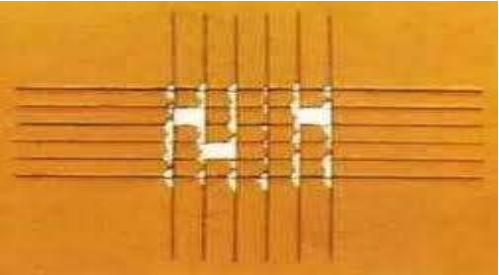

Nanoparticles

- “Nanoparticles” refers to solid particles with a size between 1 and 100 nm, often as a solid powder or dispersed in a liquid solvent.
- Must be separated by a specific distance, thus avoiding their agglomeration
- A coating is described as “nanocoating” if it contains a nanocomponent.

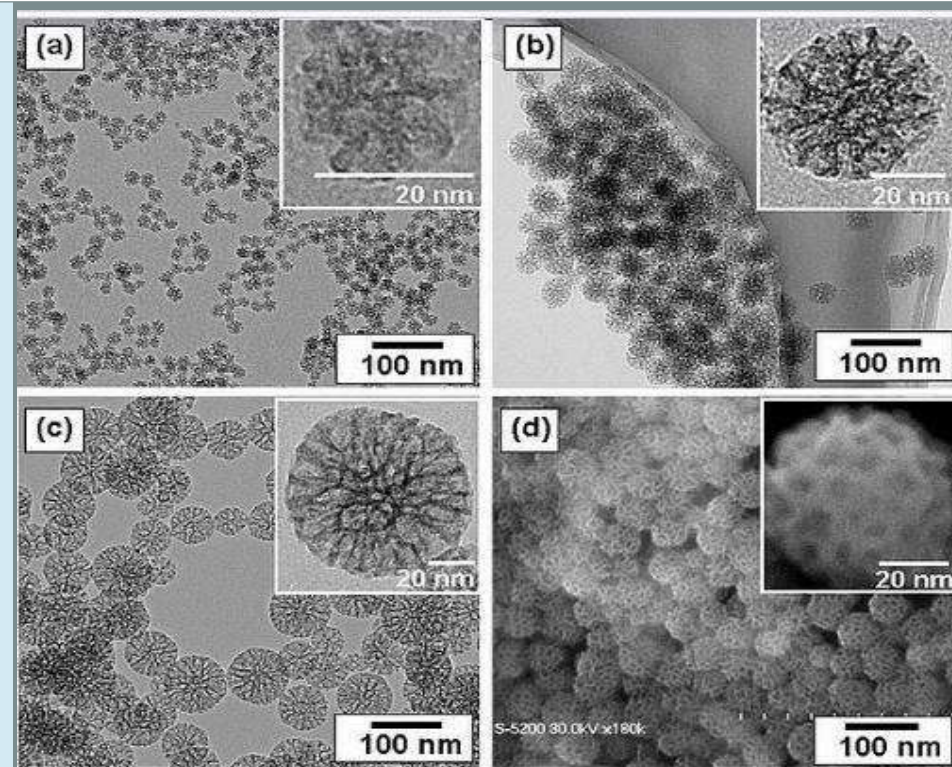



TEM (a, b, and c) images of prepared mesoporous silica nanoparticles with mean outer diameter: (a) 20nm, (b) 45nm, and (c) 80nm. SEM (d) image corresponding to (b). The insets are a high magnification of mesoporous silica particle.

<https://en.wikipedia.org/wiki/Nanoparticle>


Classification of Nanomaterials

According to chemical nature


Organic	Inorganic	Nanocomposites
<ul style="list-style-type: none">• Dendrimers• Liposome• Polymeric nanoparticles• Capsules	<ul style="list-style-type: none">• Nanowires• Nanoparticles (metal or metal oxide)• Nano-sheets• Nano-crystals• Quantum dots• Nanoshell• Carbon based structures (Fullerene, carbon nanotubes)	<ul style="list-style-type: none">• Inorganic• Organic




According to shape

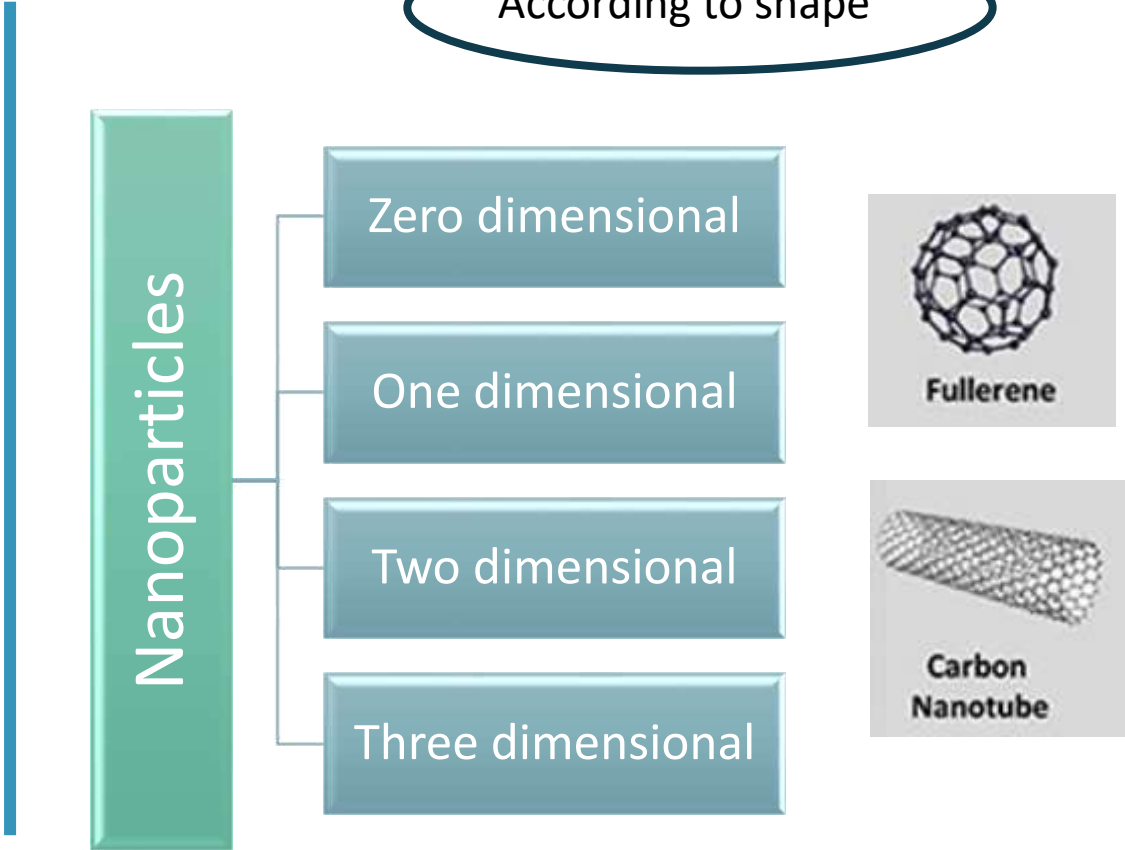

Nanoparticles

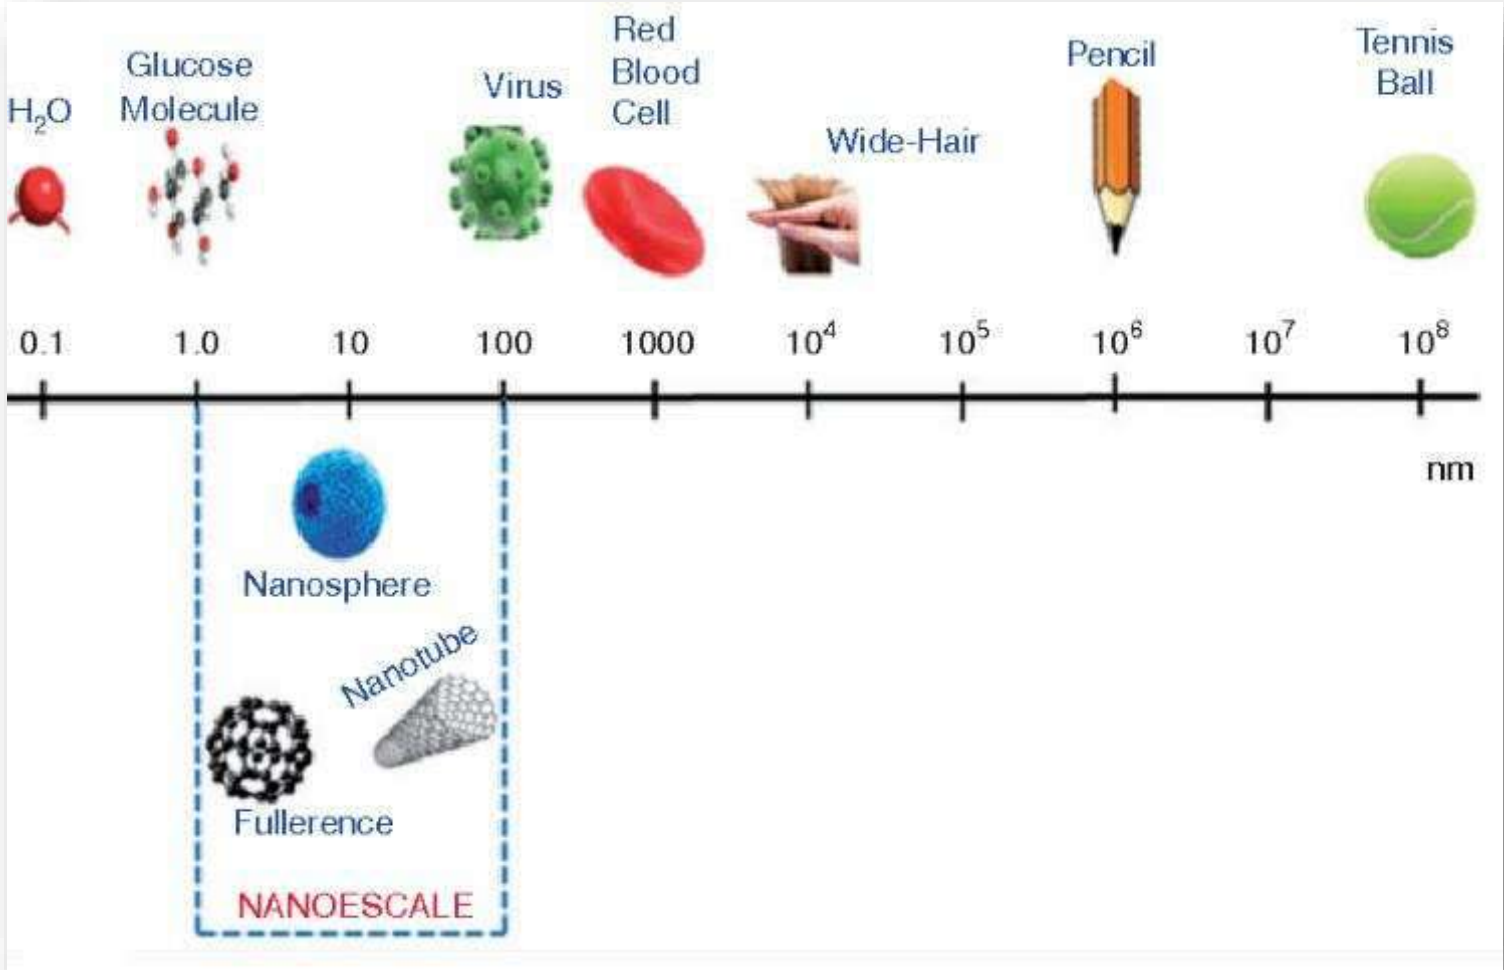

✓ **High surface area/volume ratio that** leads to thinner films, using less paint for a specific surface area

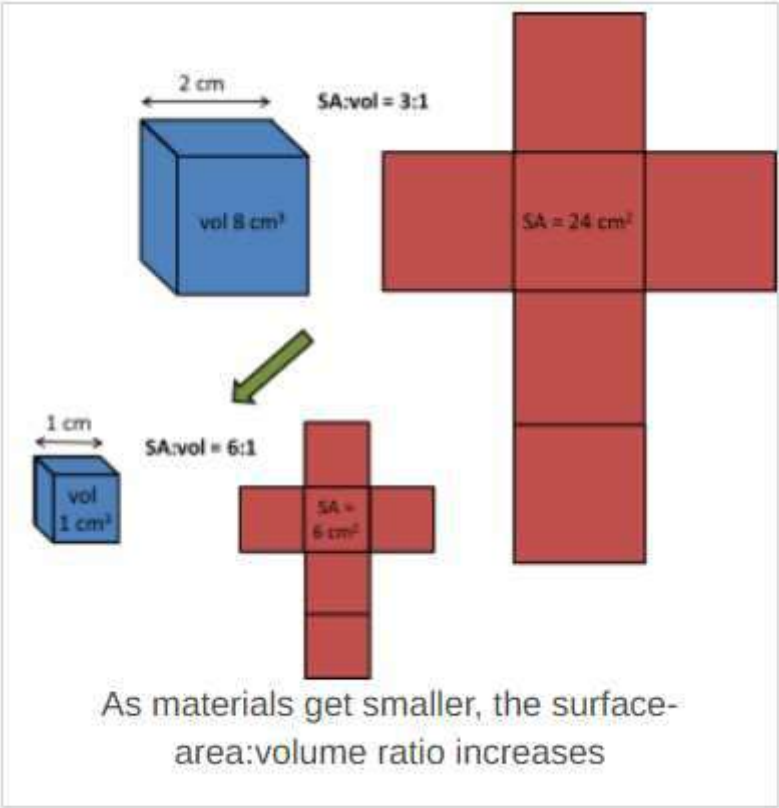


<https://chembam.com/definitions/nanotechnology/>

4



Scratch Resistant Wood Coatings

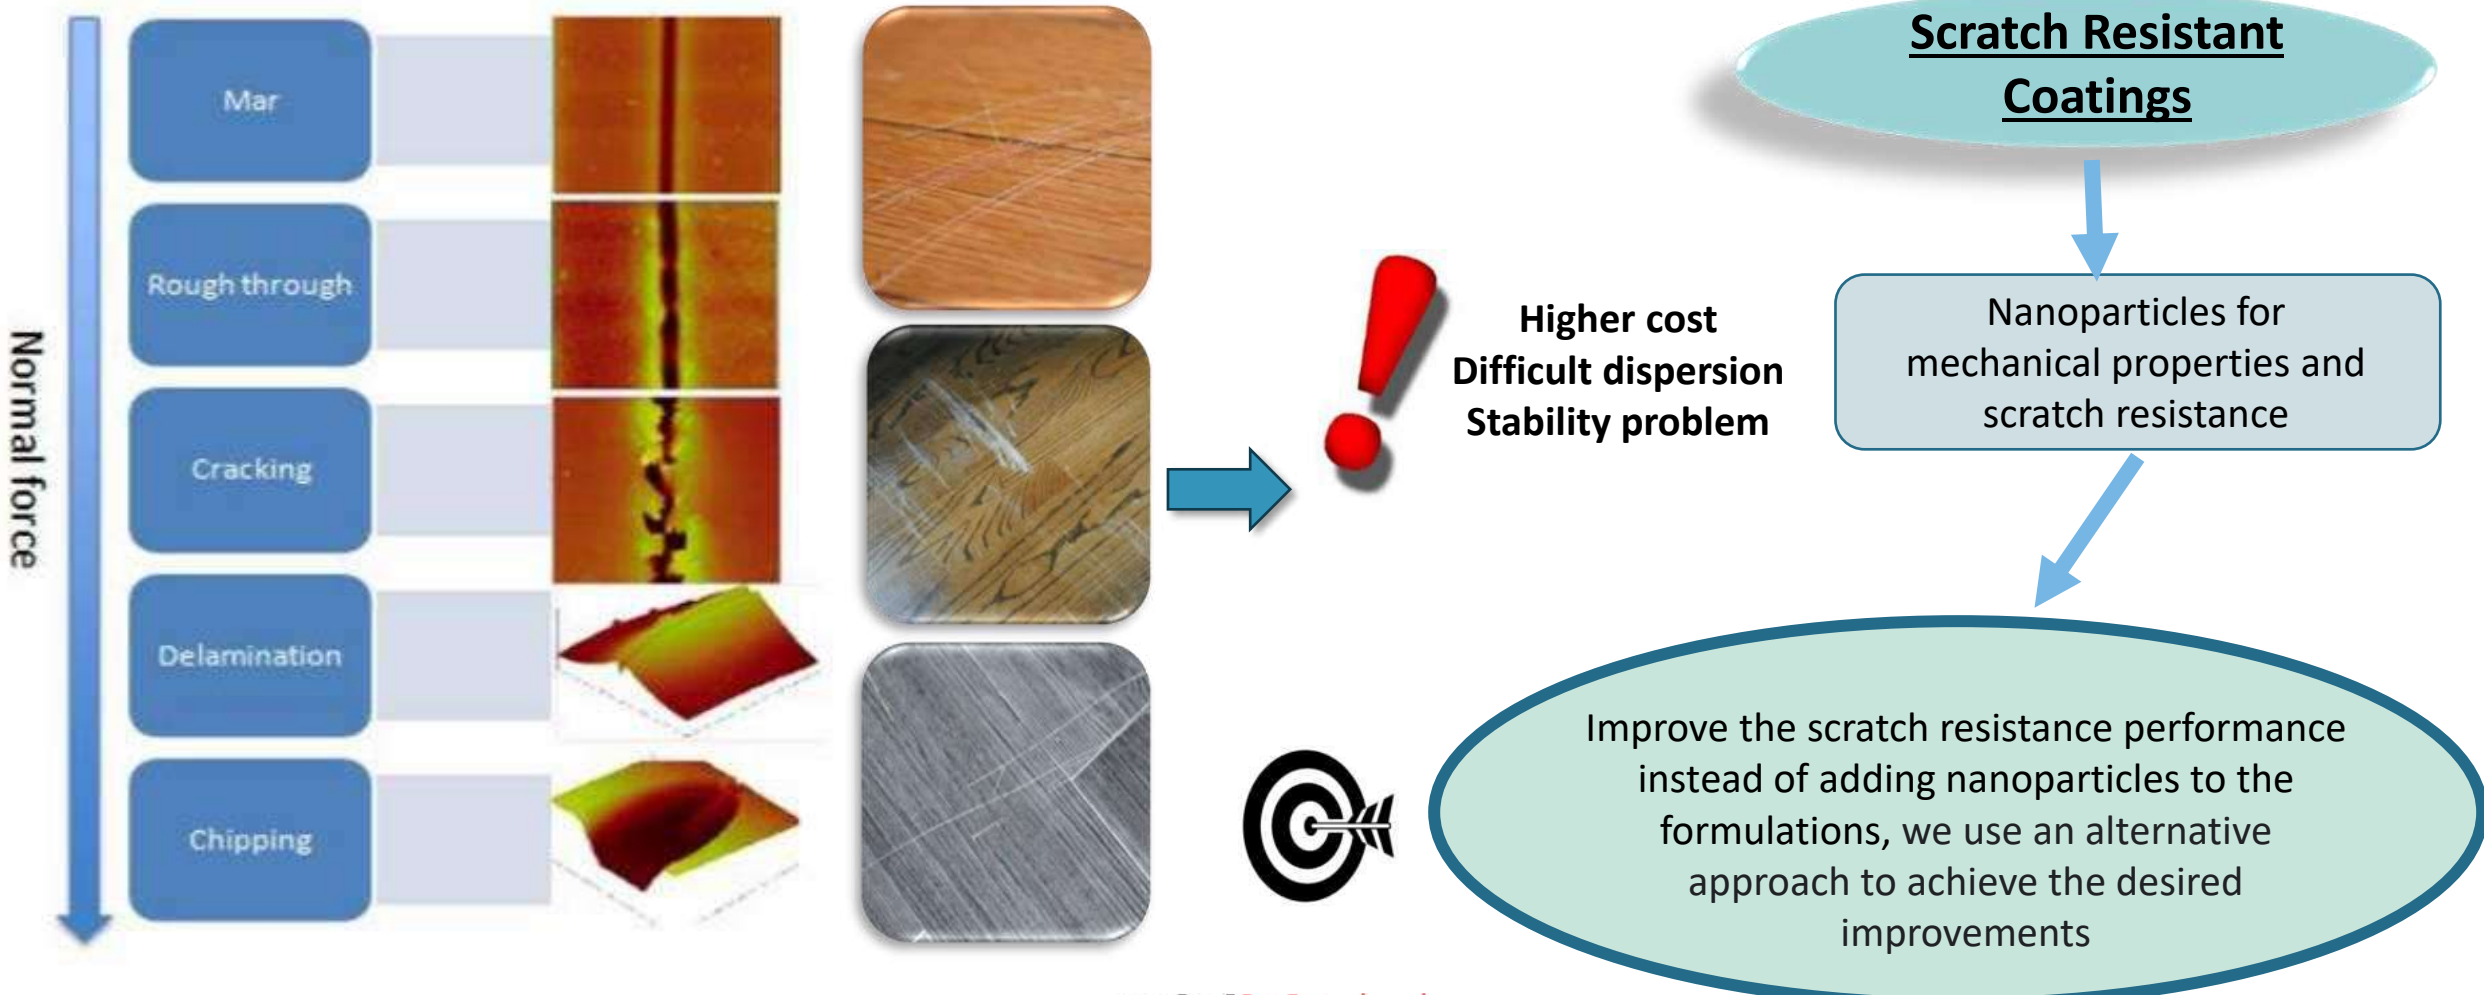

Preparing Steps of UV Curable Formulations

Determination of inorganic additives (IA-1, IA-2)

Determination of concentration of inorganic additives


Preparation of UV Acrylic Matt Varnish Topcoat (Roller) formulations

Tests & Analysis

Application Procedure of UV Formulations

UV Curing Experimental Parameters for Topcoat Applications

UV lamps (100 W)	Hg	Hg + Ga	-
Band speed of UV device	4 m/min	10 m/min	-
Wet film thickness (with bar applicator)	12 μm	24 μm	40 μm

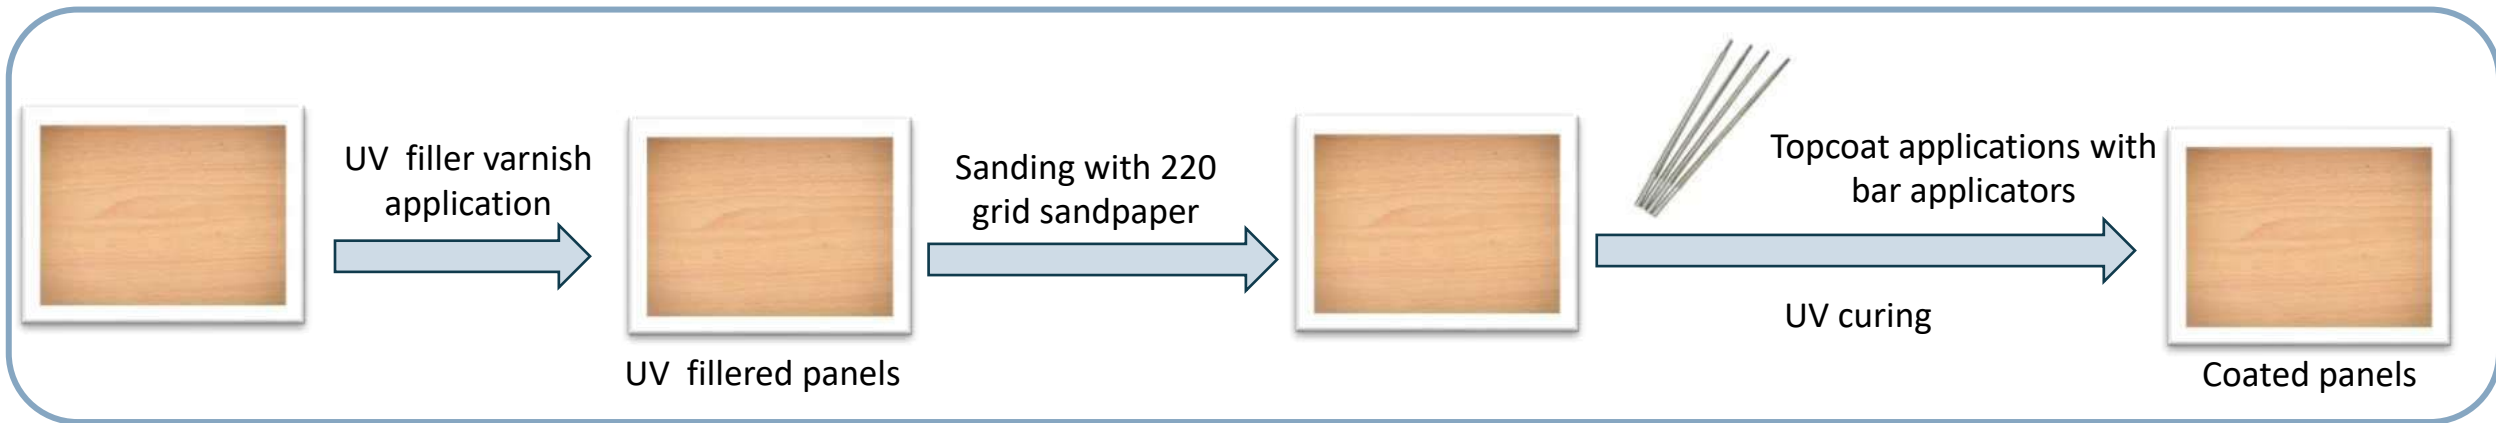





Targeted Values (wet formulations & coated panels)



Targeted values for wet formulation

Solid Content (%) TS 6035 EN ISO 3251	80-95
Density (g/cm³) ASTM D 1475-98)	1,07-1,13
Viscosity (DIN6, 20°C, sec) TS EN ISO 2431, DIN 53211)	40-45
Grinding (TS 2620 EN ISO 1524, ASTM D-1210)	6-8
Stock Stability (TS 4324)	Stable, no sagging

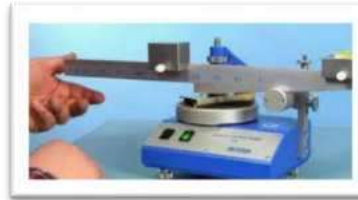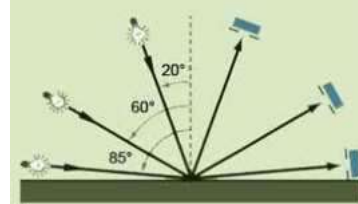

Targeted values for coated panels

Adhesion (cross-cut, DIN EN ISO 2409) (0 is the best, 5 is the worst)	0
Scratch Resistance (Erichsen Scratch Tester 413, N)	min 5
Gloss (Glossmeter, ASTM D 523, 60°)	16-24



5



RESULTS AND DISCUSSIONS

First Trials & Applications

UV Matt Topcoat Varnish (Roller coater)

Formulation	Inorganic Additive	UV Curing (Passes) (Hg lamp, 10 m/min)	Surface
Formulation-1	IA-1	1	Good
Formulation-2	IA-2	1	Bad

(with 40 µm bar applicator)

Some additional trials with IA-2



Additive Trials

Formulation	Inorganic Additive	UV Curing	Surface
		(Passes) (Hg lamp, 10 m/min)	
Formulation-3	IA-2 + Additive-1	1	Bad
Formulation-4	IA-2 + Additive-1 Additive-2	1	Good

(with 40 µm bar applicator)

First Trials & Applications

Concentration Trials of IA-2

Formulation	Inorganic Additive	Concentration of Inorganic Additive	UV Curing (Passes) (Hg lamp, 10 m/min)	Surface
Formulation-5	IA-2 + Additive-1 Additive-2	Higher	1	Good
Formulation-6	IA-2 + Additive-1 Additive-2	Lower	1	Better

(with 40 µm bar applicator)



Wet Film Thickness Trials (Formulation-6)

		STD	Formulation-6 (IA-2)
Wet film thickness 12 µm (bar applicator) Hg + Ga		4 m/min 1 Pass	4 m/min 1 Pass
	Scratch resistance (Erichsen, N)	4 N	3 N
		STD	Formulation-6 (IA-2)
		4 m/min 2 Passes	4 m/min 2 Passes
	Scratch resistance (Erichsen, N)	4 N	3 N
Wet film thickness 24 µm (bar applicator) Hg + Ga		STD	Formulation-6 (IA-2)
		4 m/min 1 Pass	4 m/min 1 Pass
	Scratch resistance (Erichsen, N)	4 N	3-4 N
		STD	Formulation-6 (IA-2)
	Scratch resistance (Erichsen, N)	4 m/min 2 Passes	4 m/min 2 Passes
		4 N	3-4 N
Wet film thickness 40 µm (bar applicator) Hg + Ga		STD	Formulation-6 (IA-2)
		4 m/min 1 Pass	4 m/min 1 Pass
	Scratch resistance (Erichsen, N)	4 N	The surface is bad, drying problem
		STD	Formulation-6 (IA-2)
	Scratch resistance (Erichsen, N)	4 m/min 2 Passes	4 m/min 2 Passes
		4 N	The surface is bad, drying problem

Scratch Test Results

Before Scratch Test

After Scratch Test

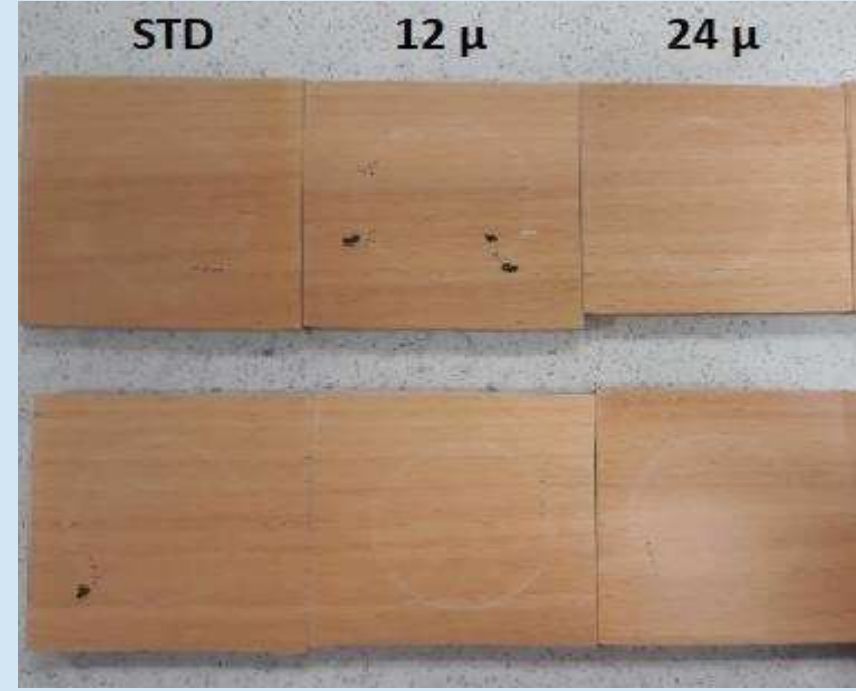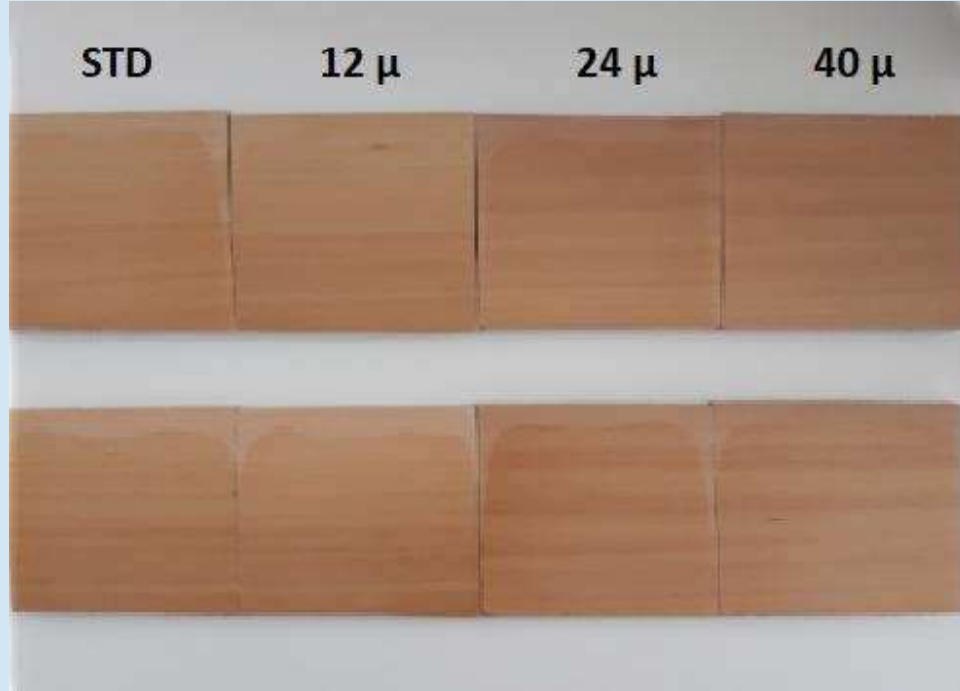

Trials with (IA-1) and (IA-2) at Lower Concentration

Wet film thickness - 24 µm (bar applicator)

Formulations (1 Pass, 4 m/min Hg + Ga)	Concentration of Inorganic Additive	Scratch Resistance (Erichsen, N)	Evaluation of Surface
---	--	-------------------------------------	-----------------------

STD

-

4

Slightly mar marks

IA-1 + Additive-1 Additive-2	Lower	5	Surface touch is very close to STD
---------------------------------	-------	---	---------------------------------------


IA-2 + Additive-1
Additive-2

Lower

3-4

Slightly mar marks

Gloss Measurements of Trials with (IA-1) and (IA-2) at Lower Concentration

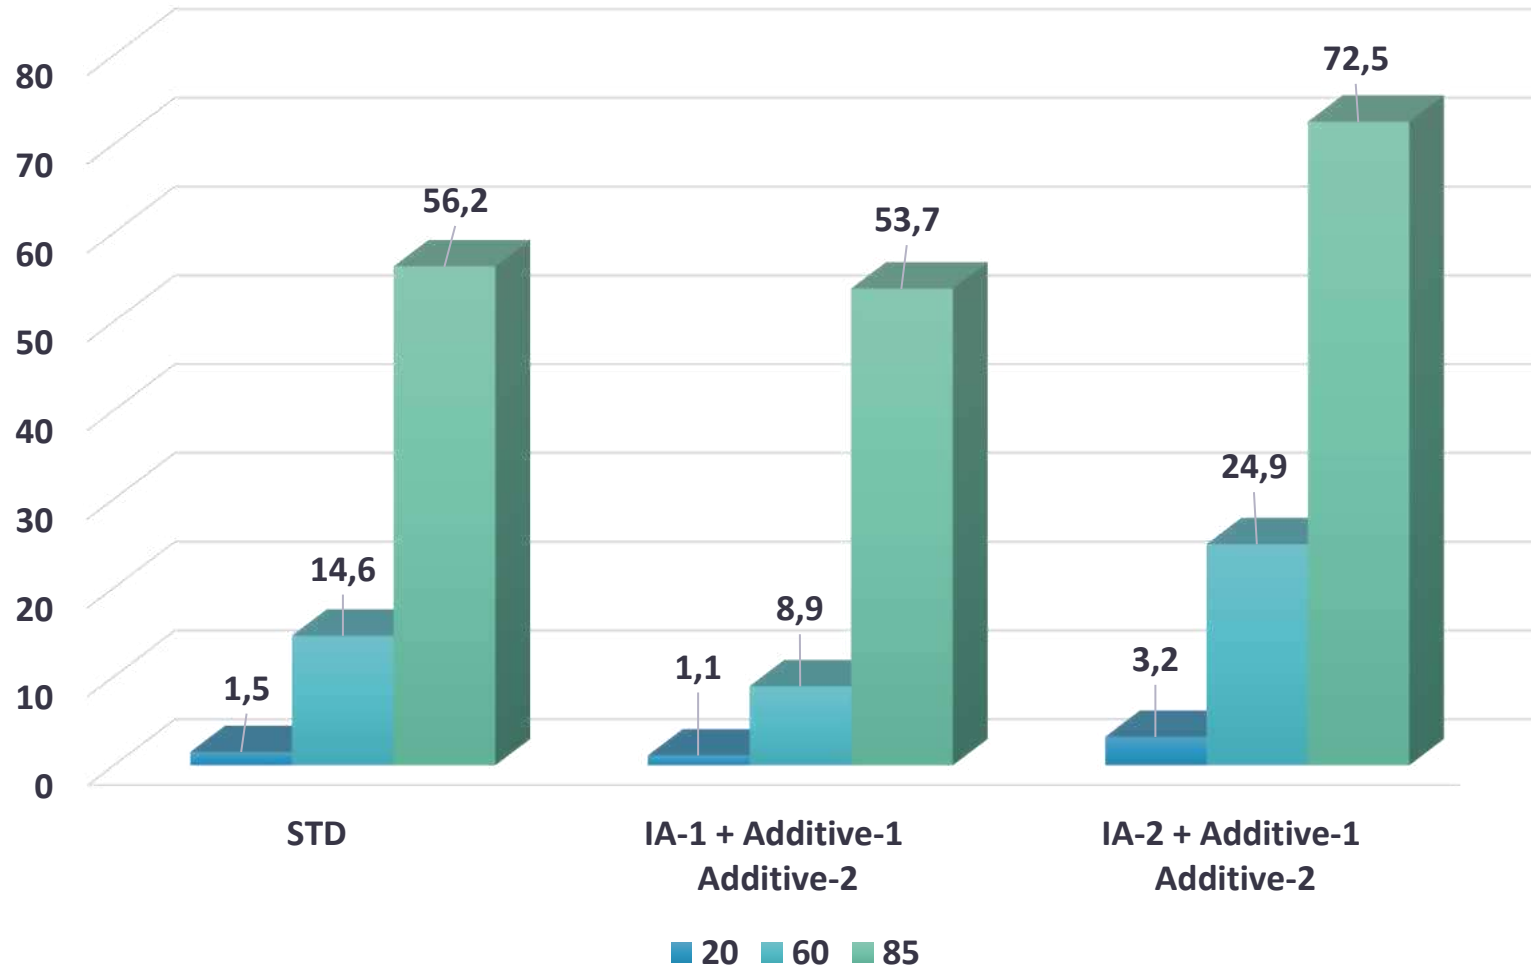


Panels After Scratch Test

STD	IA-1 + Additive-1 Additive-2	IA-2 + Additive-1 Additive-2
		

Tests and Analysis (Laboratory Trials)

UV curable matt varnish formulations (for roller applications) were prepared

IA-1 + Additive-1
Additive-2

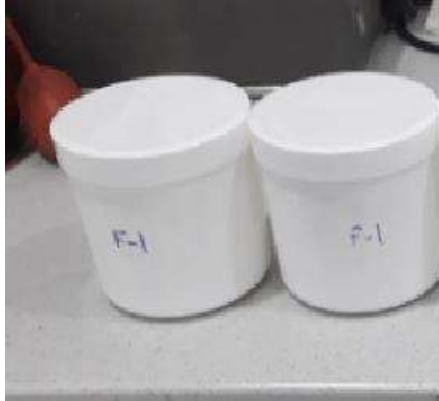

Analysis for wet formulation	Targeted Values	Results
Solid Content (%) (TS 6035 EN ISO 3251)	80-95	85-95
Density (g/cm ³) (ASTM D 1475-98)	1,07-1,13	1,09-1,12
Viscosity (DIN6, 20°C, sec) (TS EN ISO 2431, DIN 53211)	40-45	42-45
Grinding (TS 2620 EN ISO 1524, ASTM D-1210)	6-8	6-7
Stock Stability (TS 4324)	Stable, no sagging	Stable, no sagging


Coated Panel Tests (Laboratory Trials)

Wet film thickness - 24 μm (bar applicator)

Formulations (1 Pass, 4 m/min Hg + Ga)	Adhesion	Scratch Resistance (Erichsen, N)
STD	0	4
IA-1 + Additive-1+ Additive-2	0	5
IA-1 + Additive-1+ Additive-2+ Additive-3	1	4

Gloss Measurements of Coated Panels (IA-1)

Wet film thickness - 24 μm (bar applicator)

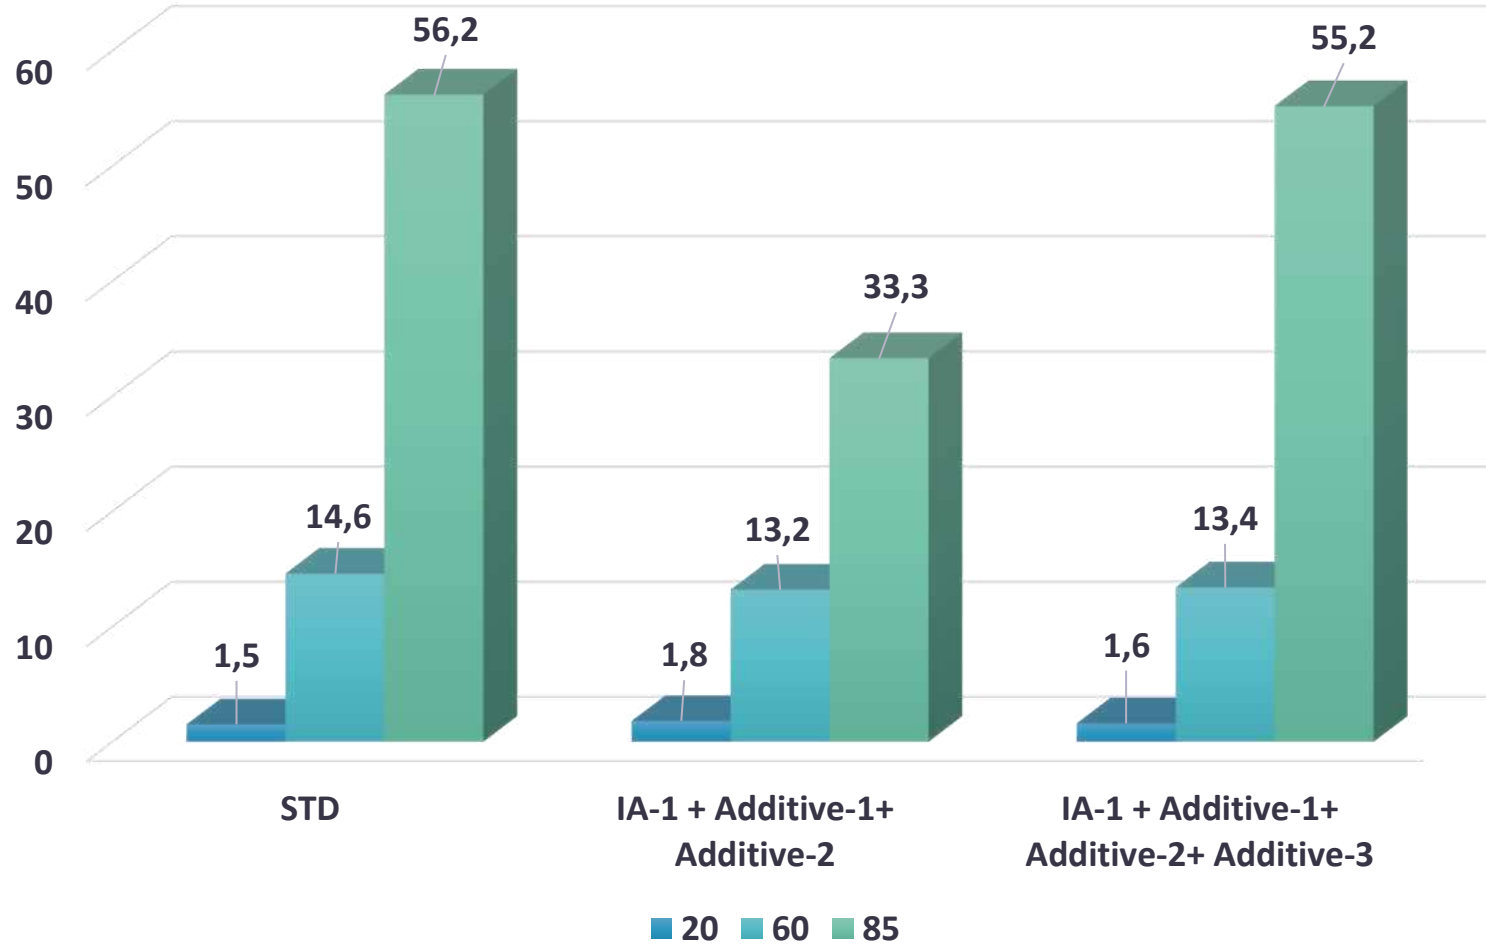



Coated Panel Tests (Laboratory Trials)

Wet film thickness - 24 μm (bar applicator)

STD	IA-1 + Additive-1 + Additive-2	IA-1 + Additive-1 + Additive-2+ Additive-3
		



SEM Analysis Results

UV Curable Coatings with IA-1

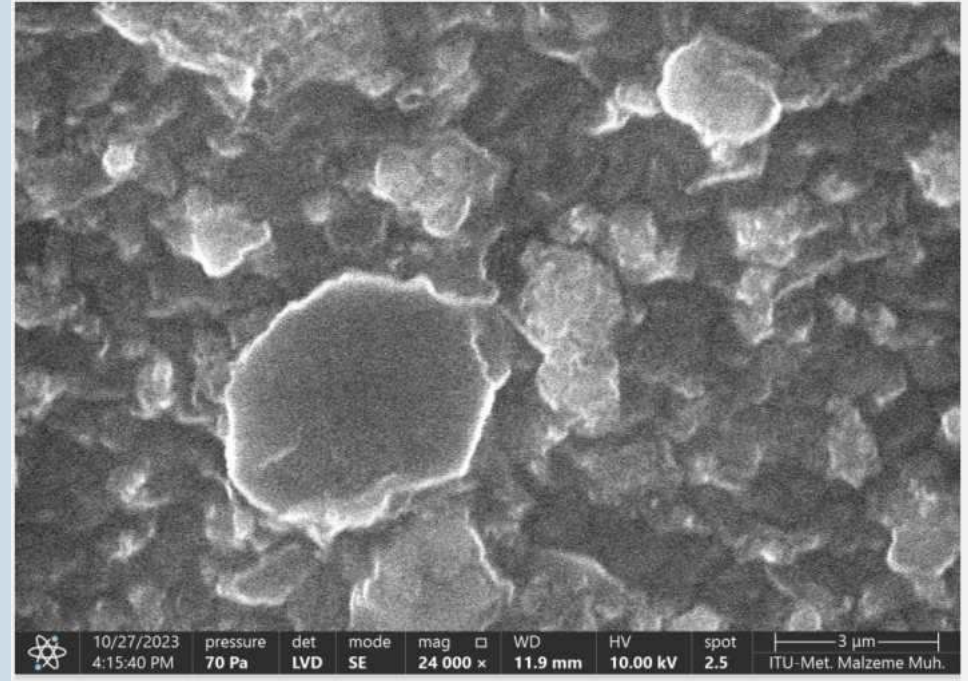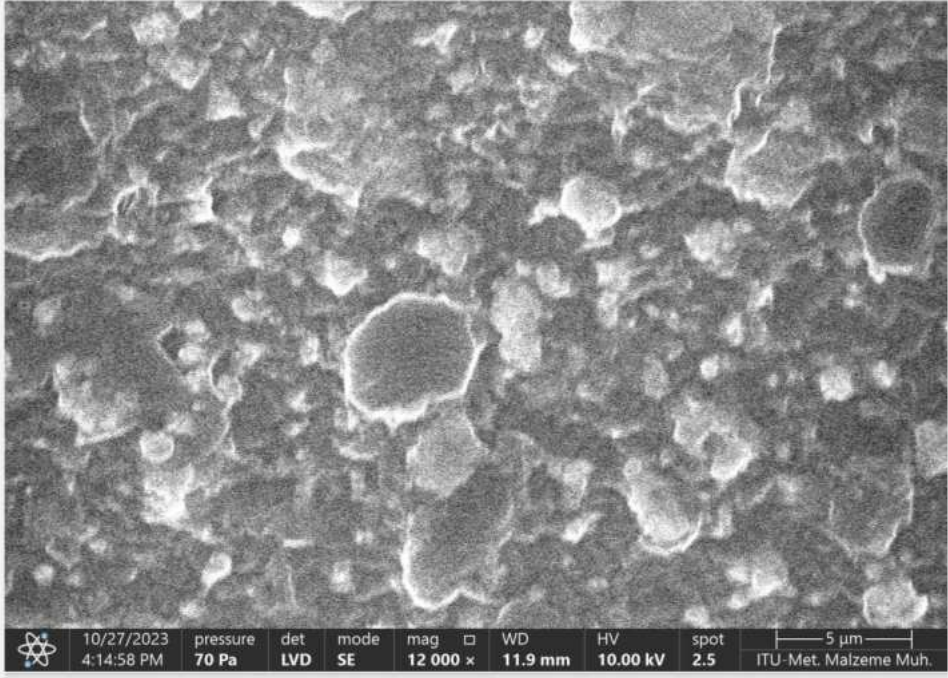


SEM Analysis Results

UV Curable Coatings with IA-2

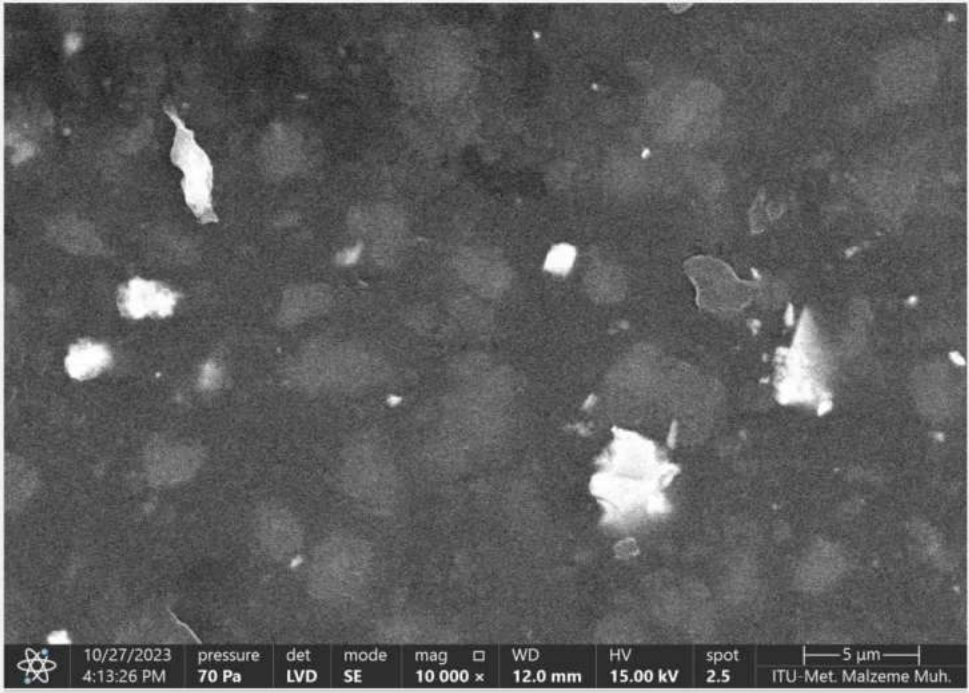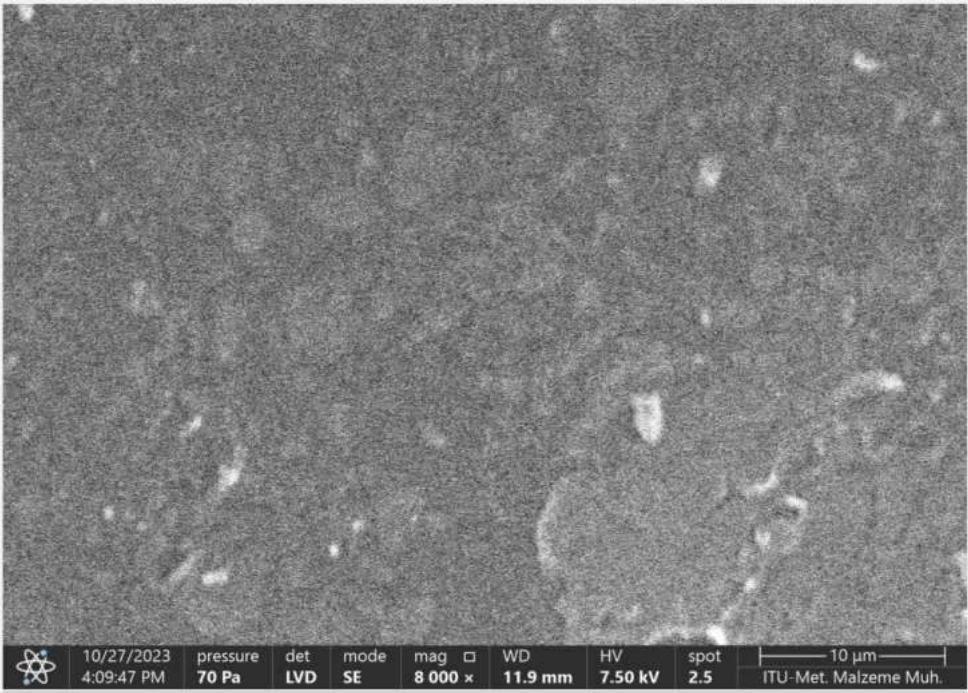

6

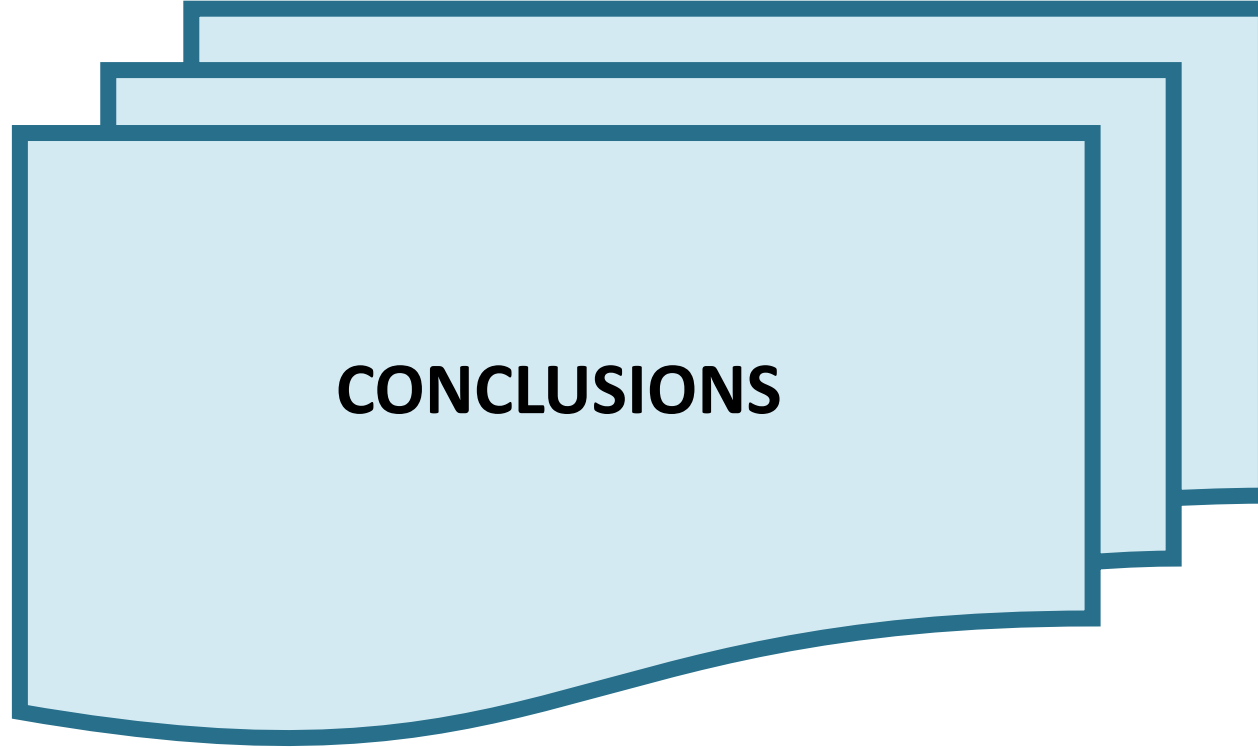

CONCLUSIONS

Conclusions

To improve the scratch resistance performance instead of adding nanoparticles to the formulations an alternative approach was tried

UV Acrylic Matt Varnish Topcoat formulations were prepared with different inorganic additives

Effects of different factors (band speed, wet film thickness, concentration of inorganic additives) on UV curable product properties were investigated

All wet formulation and coated panel tests were performed and compared to STD formulation

Surface analysis of coated panels were investigated with SEM analysis



Conclusions

	STD	IA-1 + Additive-1+ Additive-2	IA-1 + Additive-1+ Additive-2+ Additive-3
Surface properties	Fully cured and smooth	Fully cured and smooth	Fully cured and smooth
Adhesion (cross-cut, DIN EN ISO 2409)	0	0	1
Gloss (Glossmeter, ASTM D 523, 60°)	14,6	13,2	13,4
Scratch Resistance (Erichsen Scratch Tester 413, N)	4	5	4

References

- Rajkumar Singh Rawata, Nidhi Chouhana, Meenu Talwara, Rajendra Kumar Diwanb, Ajay Kumar Tyagia (2019). "UV coatings for wooden surfaces". Prog. in Org. Coat. 135:490-495.
- A self-matting waterborne polyurethane coating with admirable abrasion-resistance, Zhixia Lin, Zhe Suna, Chengping Xub, Aiqin Zhanga, Jun Xiang and Haojun Fan, RSC Adv., 2021, 11, 27620-27626, DOI: [10.1039/D1RA03738B](https://doi.org/10.1039/D1RA03738B) (Paper)
- F. Karasu, N. Arsu, S. Jockusch, and N. J. Turro, "Mechanistic studies of photoinitiated free radical polymerization using a bifunctional thioxanthone acetic acid derivative as photoinitiator," Macromolecules, vol. 42, no. 19, pp. 7318–7323, 2009.
- L. Cokbaglan, N. Arsu, Y. Yagci, S. Jockusch, and N. J. Turro, "2-mercaptothioxanthone as a novel photoinitiator for free radical polymerization," Macromolecules, vol. 36, no. 8, pp. 2649–2653, 2003.
- Prospects of Nanostructure Materials and Their Composites as Antimicrobial Agents, Anupriya Baranwal, Ananya Srivastava, Pradeep Kumar, Vivek K. Bajpai, Pawan K. Maurya, Pranjal, Chandra, Front. Microbiol., 09 March 2018, MINI REVIEW article Sec. Antimicrobials, Resistance and Chemotherapy, Volume 9 - 2018 | <https://doi.org/10.3389/fmicb.2018.00422>
- Handbook of Nanomaterials for Manufacturing Applications, Micro and Nano Technologies, CHAPTER 3: Nanomaterials in coatings: an industrial point of view, Jessica Vidales-Herrera and Israel López, Pages 51-77 (2020).
- <https://www.pcimag.com/articles/109176-prime-the-way-to-anticorrosion-coating-durability>
- Photopolymerization Reactions: On the Way to a Green and Sustainable Chemistry, Appl.Sci. 2013, 3, 490-514.
- <https://epa.gov>
- <https://chembam.com/definitions/nanotechnology/>
- <https://en.wikipedia.org/wiki/Nanoparticle>

Acknowledgement

- BOSAD, ChemMedia and Paintistanbul Congress 2023 Organization & Scientific Committee
- Prof. Dr. Nergis ARSU – Yildiz Technical University
- The board of directors and management Kayalar Kimya San. ve Tic. A.Ş.
- Alin GÜÇTAŞ, Ebru YILDIRIM, Samet DALGA, Eyüp Ensar SARIYILDIZ - Yildiz Technical University
- NARSU Research Group
- Ebru ERGÜVEN – Deniz ER -Kayalar Kimya R&D Center
- Kayalar Kimya R&D and Application & Simulation Team
- All participants of congress and all listeners

THANK YOU FOR YOUR ATTENTION..

